


Sumikaflex 450HQ

| | | |
|------------------------------|---|-------------|
| Copolymer type: | Ethylene-Vinyl acetate Copolymer Emulsion | |
| Properties: | S-450HQ is high viscosity emulsion. It has miscibility for any additive. It has good adhesion. Its viscosity is easily increased by organic solvent or thickener. It has good properties for adhesion of wood, especially for wood or decorative laminated plywood. | |
| Main application: | Adhesive use Carton Mortar | |
| Physical properties : | | |
| Appearance | | Milky white |
| Solid content (%) | | 55 ± 1 |
| Viscosity (mPa·s) | | 2000 – 4000 |
| pH | | 4 – 7 |
| Ave. particle size (µm) | | 0.7 |
| Density (g/cm ³) | | 1.07 |
| MFT (°C) | | 0 |
| Particle charge | | Nonionic |
| Mechanical stability | | Good |
| Tg (°C) | | 0 |
| Tensile strength (MPa) | | 13.0 |
| Elongation (%) | | 540 |

< Technical Information of Sumikaflex 450HQ >

1. Grade position

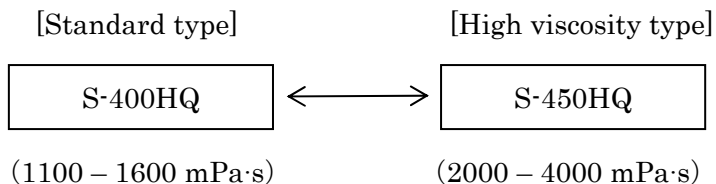

2. Emulsion properties

| | | Emulsion properties |
|----------------------|----------------------|---------------------|
| Appearance | | Milky white |
| Solid content | (%) | 55 ± 1 |
| Viscosity | (mPa·s) | 2000 – 4000 |
| pH | | 4 – 7 |
| Ave. particle size | (μm) | 0.7 |
| Density | (g/cm ³) | 1.07 |
| MFT | (°C) | 0 |
| Particle charge | | Nonionic |
| Mechanical stability | | Good |
| Tg | (°C) | 0 |

3. Film properties

(1) Tensile strength

| | | S-450HQ | S-400HQ | S-460HQ |
|-----|----------------|---------|---------|---------|
| Dry | Elongation (%) | 540 | 550 | 620 |
| | Strength (MPa) | 13.0 | 12.7 | 13.0 |
| Wet | Elongation (%) | 590 | 600 | 660 |
| | Strength (MPa) | 3.8 | 3.3 | 3.2 |

Test method

Thickness of film: 0.15 mm

Shape of film: Dumbbell No.3

Film forming condition and aging: 23°C × 65%RH × 7 days

Measurement speed: 500 mm/min

(2) Water or alkali liquid of resistance of film

| | | S-450HQ | S-400HQ | A-460HQ |
|--------------------------|----------------|---------|---------|---------|
| Water resistance | Elusion (%) | 4 | 5 | 9 |
| | Absorption (%) | 16 | 16 | 19 |
| Alkali liquid resistance | Elusion (%) | 12 | 9 | 12 |
| | Absorption (%) | 23 | 20 | 28 |

Test method


Thickness of film: 0.15 mm

Water resistance: Film in water for 4 days at 23 °C

Alkali liquid of resistance: Film in 1 N NaOH for 4 days at 23 °C

4. Modification of physical properties

(1) Toluene thickening

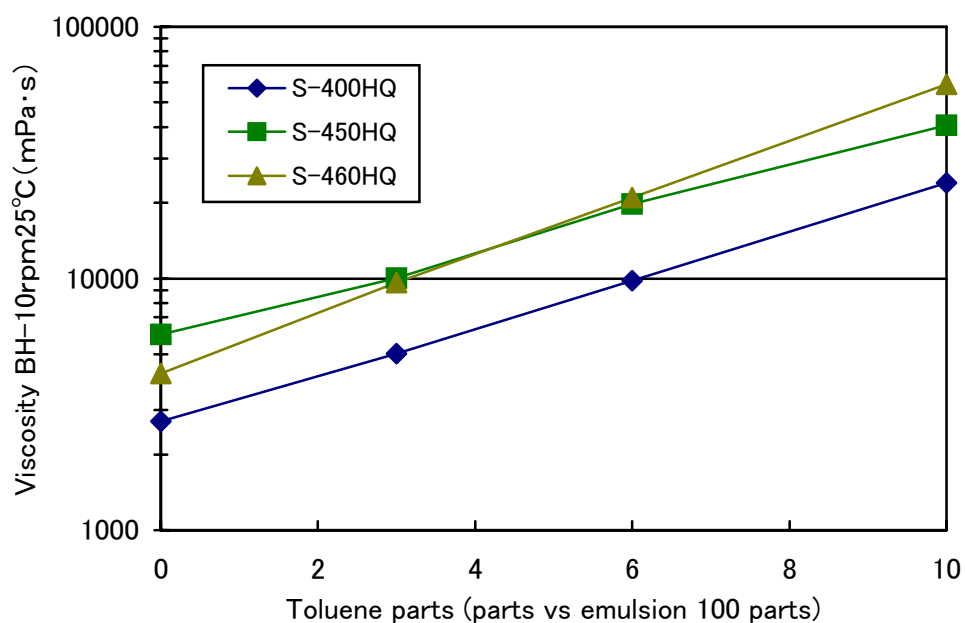

5. Applications

(1) Plastic sheet to plywood

| | Toluene additive (parts) | Peel strength (N/25 mm) | | 60°C Creep (mm/hr) |
|---------|--------------------------|-------------------------|-----|--------------------|
| | | Dry | Wet | |
| S-450HQ | 0 | 52 | 25 | 6 |
| | 6 | 50 | 15 | 40 |
| | 10 | 45 | 14 | 55 |
| S-400HQ | 0 | 53 | 21 | 5 |
| | 6 | 49 | 15 | 40 |
| | 10 | 43 | 13 | 58 |
| S-460HQ | 0 | 50 | 19 | 4 |
| | 6 | 48 | 16 | 38 |
| | 10 | 46 | 16 | 50 |

Test method

Plastic sheet: Thin Flexible PVC sheet

Plywood: Lauan JAS Type 1 3 ply 3 mm thickness

Adhesive formulation: Emulsion / Toluene = 100/0, 6, 10 parts

Spread: Wet 130 g/m²

Pressing: 50 kg/30 × 30 cm², 24 hours (23°C × 65%RH)

Aging: 6 days after pressing (23°C × 65%RH)

Peeling strength (dry condition): Peel speed 100 mm/min, Peel angle 180°

Peeling strength (wet condition): Wetting test piece after test piece in water for 20 hours, peel speed and angle are the same as dry condition

60°C Creep: At 60°C, 500g weight for 90° angle of static load test

(2) Plastic sheet to particle board

| | Peel strength (N/25 mm) | | 60°C Creep (mm/10 min) |
|---------|-------------------------|-----|------------------------|
| | Dry | Wet | |
| S-450HQ | 34 | 27 | 20 |
| S-400HQ | 35 | 27 | 18 |
| S-460HQ | 38 | 31 | 19 |

Test method

Particle board: JIS A5908 200-U type

Plastic sheet: Thin Flexible PVC sheet

Spread: Wet 110 g/m²

Pressing: 50 kg/30 × 30 cm² for 24 hours (23°C × 65%RH)

Aging: 6 days after pressing (23°C × 65%RH)

Peel speed: 50 mm/min

60°C Creep: At 60°C, 1000 g weight for 90° angle of static load test, measure the peeled length

(3) Setting time for several materials

| | | S-450HQ | S-400HQ | S-460HQ |
|---|-------------------------|---------|---------|---------|
| A | Craft paper/Craft paper | 9 sec | 12 sec | 13 sec |
| B | Craft paper/Aluminum | 23 sec | 23 sec | 23 sec |
| C | Craft paper/PVC | 12 sec | 18 sec | 20 sec |
| D | Particle board/PVC | 50 min | 55 min | 50 min |
| E | Gypsum/PVC | 3 min | 4 min | 3 min |

Test method

Adhesive: A – B (emulsion only), C – E (emulsion and Toluene 6 parts mixing)

Spread: A – C: Wet 50 g/m² D – E: Wet 110 g/m²

Test room condition: 23°C × 65%RH

Measurement: Coat the substrate with adhesive as soon as possible, the substrate and the coated substrate will be bonded, then peel the substrate at a constant time. Measured the time when the substrate is completely broken.

(4) Gummed up property

| | Gummed up time (min) |
|---------|----------------------|
| S-450HQ | 61 |
| S-400HQ | 75 |
| S-460HQ | 52 |

Test method

Role coater Speed: 85 m/min